



**Night School 27:
Fundamentals of
Welding and Bolting**

Thank you for joining our live webinar. We will begin shortly. Please standby.

Session 1 – Introduction and Welding Processes
September 27, 2021 | Curtis Decker



Smarter.
Stronger.
Steel.




AISC Live Webinars

Today's live webinar will begin shortly. Please stand by.

Today's audio will be broadcast through the internet. Please be sure to turn up the volume on your speakers.

Please type any questions or comments in the Q&A window.




AISC Live Webinars

AIA Credit

AISC is a Registered Provider with The American Institute of Architects Continuing Education Systems (AIA/CES). Credit(s) earned on completion of this program will be reported to AIA/CES for AIA members. Certificates of Completion for both AIA members and non-AIA members are available upon request.

This program has been submitted for AIA/CES for continuing professional education. As such, it does not include content that may be deemed or construed to be an approval or endorsement by the AIA of any material of construction or any method or manner of handling, using, distributing, or dealing in any material or product.

Questions related to specific materials, methods, and services will be addressed at the conclusion of this presentation.




AISC Live Webinars

Copyright Materials

This presentation is protected by US and International Copyright laws. Reproduction, distribution, display and use of the presentation without written permission of AISC is prohibited.

© The American Institute of Steel Construction 2021

The information presented herein is based on recognized engineering principles and is for general information only. While it is believed to be accurate, this information should not be applied to any specific application without competent professional examination and verification by a licensed professional engineer. Anyone making use of this information assumes all liability arising from such use.




AISC Live Webinars

Course Description

**NS27.1 – Welding Part 1
Introduction and Welding Processes
September 27, 2021**


This session will consist of a review of applicable welding codes, the basics of welded joints and weld types, and required weld metal strength levels. Details for welded connection details will be discussed, including the basic criteria to be used to determine weld throat dimensions.



AISC Live Webinars

Learning Objectives

- Identify standards related to welding.
- Compare and contrast various arc welding processes.
- Define various welding and thermal cutting processes.
- Compare and contrast various joints and weld types.



Night School 27: Fundamentals of Welding and Bolting



Curtis L. Decker, PhD, PE, SE, The Lincoln Electric Company

Duane K. Miller, PE, ScD, The Lincoln Electric Company

Chad Larson, LeLeune Bolt Company






Smarter. Stronger. Steel.

Night School 27: Fundamentals of Welding and Bolting

Welding Part 1: Introduction and Welding Processes
September 27, 2021


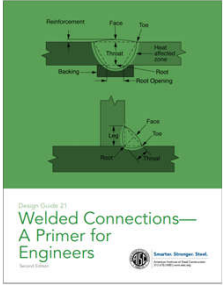
Curtis L. Decker, PhD, PE, SE, The Lincoln Electric Company



Smarter. Stronger. Steel.

AISC Design Guide 21, 2nd Edition


**Welded Connections—
A Primer for Engineers**



WELDED CONNECTIONS—A PRIMER FOR ENGINEERS

Chapter 1: Introduction

- 1.1 Importance of Welding
- 1.2 Scope of Welding
- 1.3 Welding-Related Codes and Specifications




10

WELDED CONNECTIONS—A PRIMER FOR ENGINEERS

Chapter 2: Welding and Thermal Cutting Processes

- 2.1 Introduction
- 2.2 SMAW
- 2.3 FCAW
- 2.4 SAW
- 2.5 GMAW
- 2.6 ESW/EGW
- 2.7 GTAW




11

WELDED CONNECTIONS—A PRIMER FOR ENGINEERS

Chapter 2: Welding and Thermal Cutting Processes

- 2.8 Arc Stud Welding
- 2.9 Thermal Cutting Processes
- 2.10 Water Jet Cutting




12

WELDED CONNECTIONS—A PRIMER FOR ENGINEERS

Chapter 3: Welded Connection Basics

- 3.1 Joints
- 3.2 Weld Types—General
- 3.3 Complete-Joint-Penetration Groove Welds
- 3.4 Partial-Joint-Penetration Groove Welds
- 3.5 Fillet Welds
- 3.6 Plug/Slot Welds
- 3.7 Puddle Welds




13

WELDED CONNECTIONS—A PRIMER FOR ENGINEERS

Chapter 3: Welded Connection Basics

- 3.8 Interaction of Joint Types and Weld Types
- 3.9 Selection of Weld Types
- 3.10 Required Filler Metal Strength
- 3.11 Determining Weld Strength
- 3.12 Specific Requirements for Various Joints
- 3.13 Weld Symbols




14

WELDED CONNECTION BASICS

Outline

- Applicable Codes
- Arc Welding Processes – Overview
- Welding and Thermal Cutting Processes
- Joints and Weld Types




15

WELDED CONNECTION BASICS

Outline



- Applicable Codes
- Arc Welding Processes – Overview
- Welding and Thermal Cutting Processes
- Joints and Weld Types



16

AWS D1.1

Structural Welding Code –
Steel




17

AWS D1.1: 2020 Structural Welding Code – Steel

Major sections of AWS D1.1 include the following:

- Clause 1 – General Requirements
- Clause 2 – Normative References
- Clause 3 – Terms and Definitions
- Clause 4 – Design of Welded Connections
- Clause 5 - Prequalification of WPSs
- Clause 6 - Qualification





18

AWS D1.1: 2020 Structural Welding Code – Steel

Major sections of AWS D1.1 include the following:


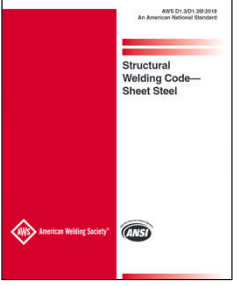
- Clause 7 – Fabrication
- Clause 8 – Inspection
- Clause 9 – Stud Welding
- Clause 10 – Tubular Structures
- Clause 11 – Strengthening and Repair of Existing Structures



19

AWS D1.3

Structural Welding Code –
Sheet Steel





20

AWS D1.3: 2018 Structural Welding Code – Sheet Steel

AWS D1.3 covers:


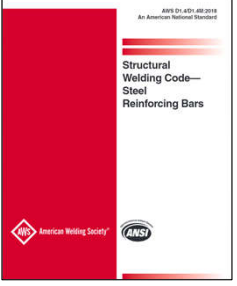
- Welding of structural sheet and strip steels, including cold-formed members equal to or less than 3/16 in. [5mm] thick.
- The primary purpose for structural steel applications: welding sheet steel decking to supporting members with puddle welds.



21

AWS D1.4

Structural Welding Code –
Steel Reinforcing Bars



22

AWS D1.4: 2018 Structural Welding Code – Steel Reinforcing Bars

AWS D1.4 covers:



- Welding of reinforcing steel (rebar) to itself
- Welding of rebar to plate or shapes, including embed plates and steel used in composite construction



23

AASHTO/AWS D1.5

Bridge Welding Code





24

AASHTO/AWS D1.5: 2020 Bridge Welding Code

AASHTO/AWS D1.5:


- Joint standard of the AWS and the American Association of State Highway Transportation Officials (AASHTO)
- Generally requires that WPS be qualified by test, with a few exceptions
- Qualification testing involves Charpy V-notch (CVN) specimens and all weld metal tensile specimens
- Nondestructive testing (NDT) requirements



25

AWS D1.6

Structural Welding Code –
Stainless Steel

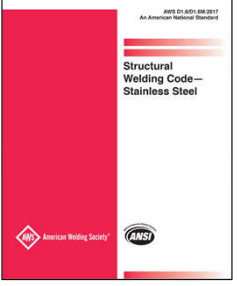



26

AWS D1.6: 2017 Structural Welding Code – Stainless Steel

AWS D1.6 covers:


- Requirements for welding various grades of stainless to stainless, as well as stainless to carbon steel



27

AWS D1.7

Guide for Strengthening and Repairing
Existing Structures





28

AWS D1.7: 2010 Guide for Strengthening and Repairing Existing Structures

AWS D1.7:

- D1.1 requires the Engineer to “establish a comprehensive plan for the work”: D1.7 can provide guidance
- Not a code, but a guide
- Provides guidance on: weldability, evaluation of existing welds, testing and sampling, heat strengthening, strengthening and damage repair



29

AWS D1.8

Structural Welding Code –
Seismic Supplement





30

AWS D1.8: 2016 Structural Welding Code – Seismic Supplement

AWS D1.8:



- Supplements AWS D1.1
- When AWS D1.8 is specified, all the provisions of AWS D1.1 still apply, unless modified or superseded by AWS D1.8
- Assumes that the structure is designed with AISC *Seismic Provisions*

31

AISC 360-16

Specification for Structural Steel Buildings



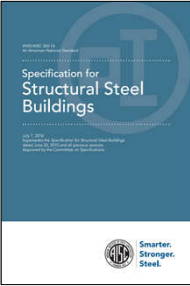


32

AISC 360-16 Specification for Structural Steel Buildings

AISC 360 addresses the following major welding-related items:

- Acceptable steel designations (Section A3.1)
- Acceptable filler metals (Section A3.5)
- Requirements for splices in heavy sections (Section J1.5)
- Beam copes and weld access holes (Section J1.6)
- Welds in combination with bolts (Section J1.8)
- Details of groove welds (Section J2.2)
- Details of fillet welds (Section J2.2)






33

AISC 360-16 Specification for Structural Steel Buildings

AISC 360 addresses the following major welding-related items:



- Available strength of welded joints (Table J2.5)
- Shop fabrication/welding issues (Section M2)
- Field erection/welding issues (Section M4)
- Weld quality control and quality assurance issues (Chapter N)
- Weld details for fatigue (Appendix 3)
- Welding issues associated with existing structures (Appendix 5)

34

AISC 341-16

Seismic Provisions for Structural Steel Buildings






35

AISC 341-16 Seismic Provisions for Structural Steel Buildings

AISC 341:


- Developed to augment the AISC *Specification*
- Adds provisions deemed necessary for high-seismic applications, where steel members are required to dissipate energy through controlled inelastic deformations in major seismic events
- For welding-related issues, primarily refers to D1.8
- Contains “grocery list” of items to be specified in contract documents, including many welding-related issues

36

AISC 358-16

Prequalified Connections for Special and Intermediate Steel Moment Frames for Seismic Applications

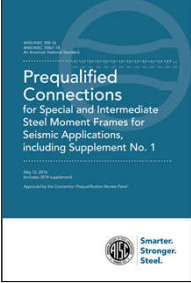

37

AISC 358-16 Prequalified Connections for Special and Intermediate Steel Moment Frames for Seismic Applications


AISC 358:

- Specifies design, detailing, fabrication, and quality criteria for connections that are prequalified in accordance with AISC *Seismic Provisions*
- For use with special moment frames (SMF) and intermediate moment frames (IMF)
- For welding-related issues, primarily refers to AISC 341
- Some prequalified connections have unique welded detail requirements (WUF-W, Endplate)

38

AISC 303-16

Code of Standard Practice for Steel Buildings and Bridges

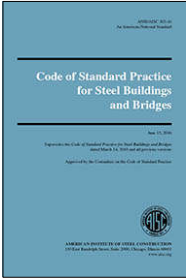

39

AISC 303-16 Seismic Provisions for Structural Steel Buildings

AISC 303 addresses these major welding-related issues:

- Overall tolerances of fabricated members and erected assemblies
- Basic tolerances for architecturally exposed structural steel (AESS)

40

Welding-Related Codes and Specifications

Other AWS D1 Codes:

- AWS D1.2/D1.2M *Structural Welding Code — Aluminum*
- AWS D1.9/D1.9M *Structural Welding Code — Titanium*

41

Welding-Related Codes and Specifications

Other AWS Standards:


- AWS A5 *Filler Metal Specifications*
- AWS A2.4 *Standard Symbols for Welding, Bracing, and Nondestructive Examination*
- AWS A3.0/A3.0M *Standard Welding Terms and Definitions*

42

WELDED CONNECTION BASICS

Outline

- Applicable Codes
- ➔ • Arc Welding Processes – Overview
- Welding and Thermal Cutting Processes
- Joints and Weld Types




43

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2010)

weld.

A localized coalescence of metals or nonmetals produced by heating the materials to the welding temperature, with or without the application of pressure, or by the application of pressure alone and with or without the use of filler metal.




44

Arc Welding Processes

Requirements for fusion:


- Atomic closeness
- Atomic cleanliness




45

Arc Welding Processes

Atomic Closeness

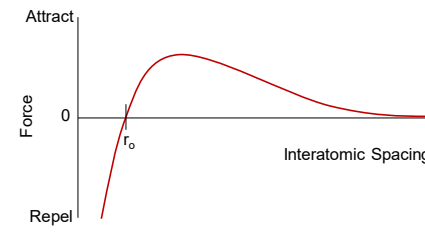




Adapted from W.F. Savage, as presented in *Weld Imperfections*, 1968



46

Arc Welding Processes




Atomic Closeness

47

Arc Welding Processes

Atomic Closeness

48

Arc Welding Processes

Atomic Closeness

Force vs. Interatomic Spacing graph showing Attract, 0, and Repel regions. A yellow bar highlights the attractive region.

49

Arc Welding Processes

Atomic Closeness

Force vs. Interatomic Spacing graph showing Attract, 0, and Repel regions. A yellow bar highlights the attractive region.

50

Arc Welding Processes

Atomic Closeness:

- Very, very close
- Gaps exist between materials, even carefully machined parts (typically 100-1000 atom diameters from peak to valley of carefully machined parts)

51

Arc Welding Processes

How to Achieve Atomic Closeness:

- Melt one material (brazing, soldering)
- Melt two or more materials (arc welding, resistance welding)
- Use pressure (with or without heat) to force closeness (forge welding, friction stir welding)

52

Arc Welding Processes

Atomic Cleanliness:

- Oxides form very rapidly
- Oxides neutralize the attractive forces
- Other contaminants: water, oil, gasses







53



Arc Welding Processes

How to Achieve Atomic Cleanliness:

- Mechanically clean the part (scraping, machining)
- Chemically clean the part (fluxes)


54

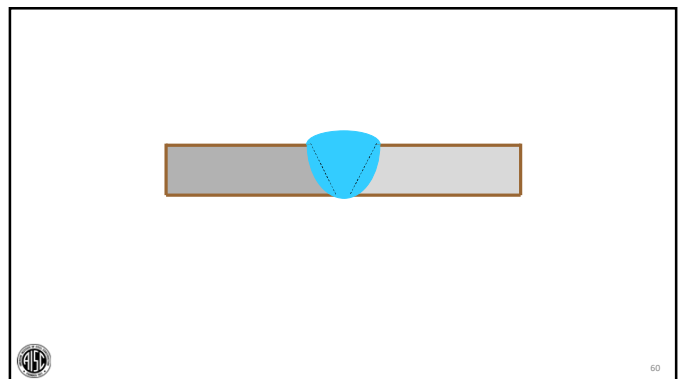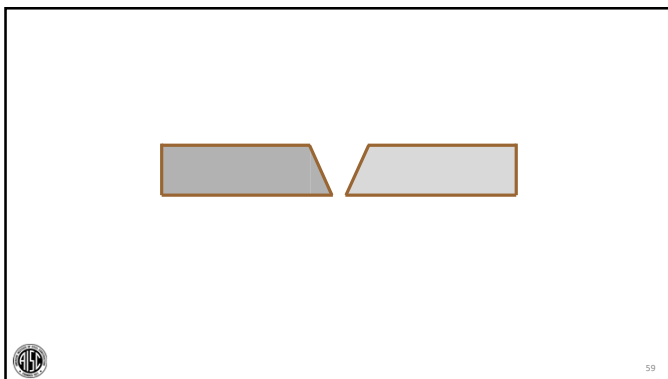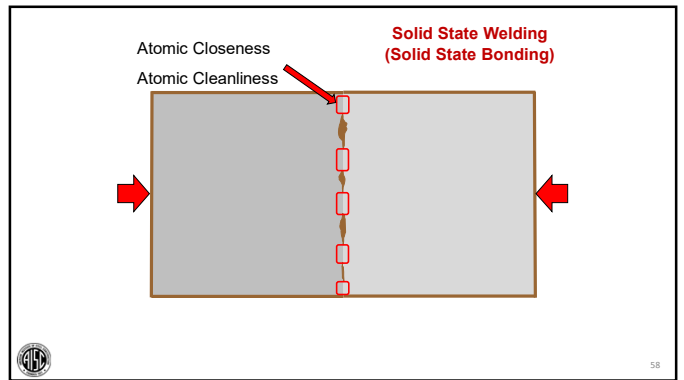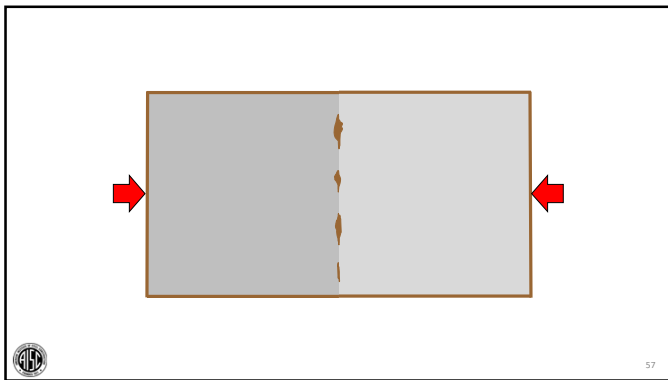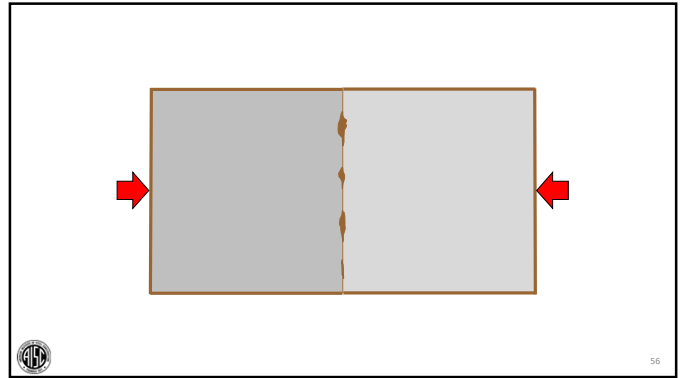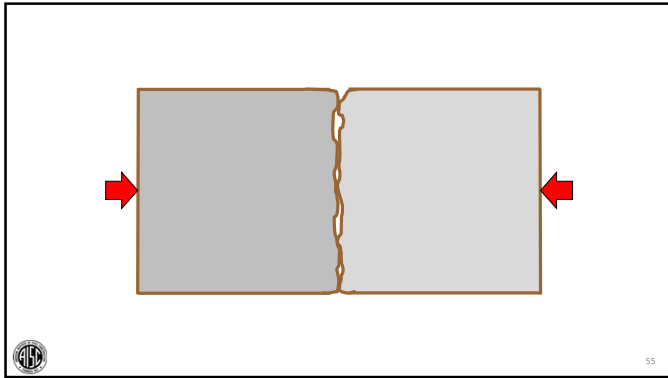

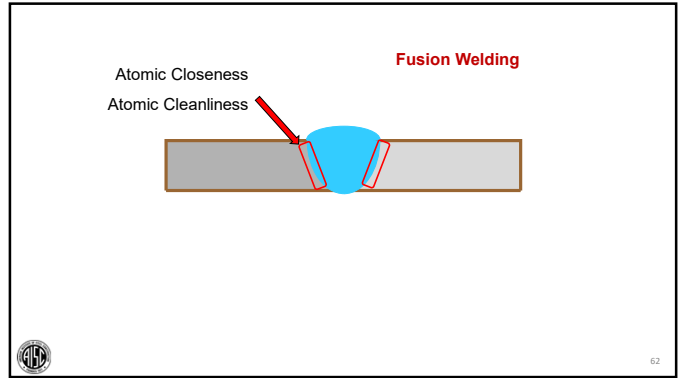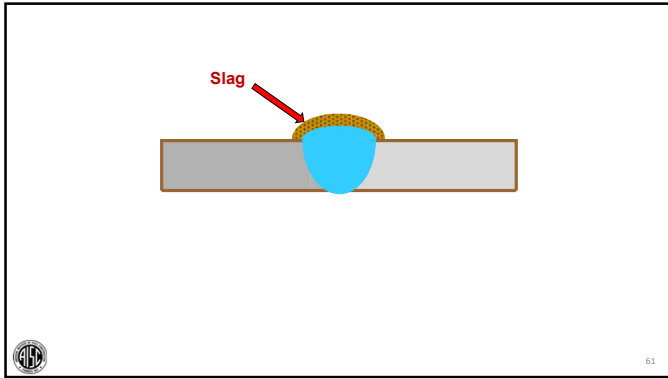

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)


fusion, fusion welding.
The melting together of filler metal and base metal, or of base metal only, to produce a weld.





The AISC logo is in the bottom left corner, and the number "63" is in the bottom right corner.


AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)

arc welding.
A group of welding processes producing coalescence of workpieces by melting them with an arc. The processes are used with or without the application of pressure and with or without filler metal.



The AISC logo is in the bottom left corner, and the number "64" is in the bottom right corner.

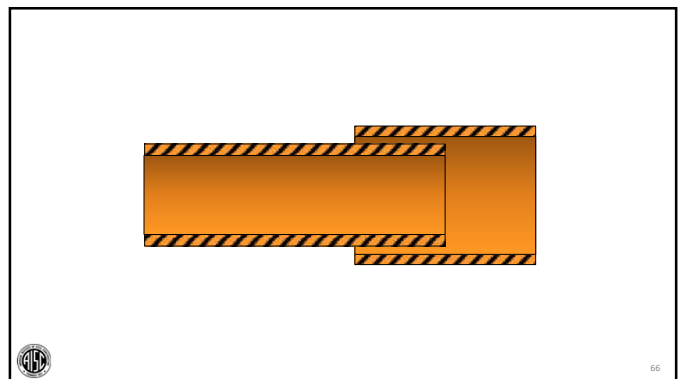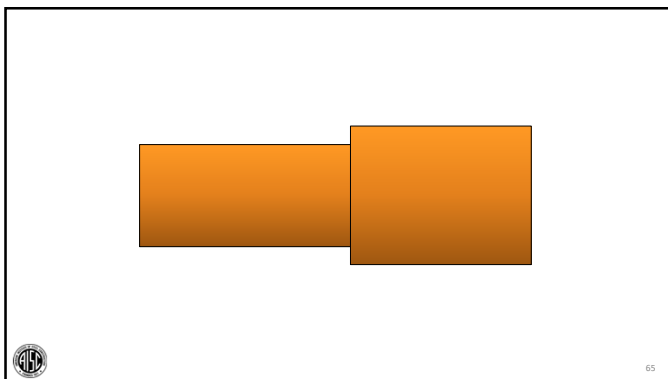

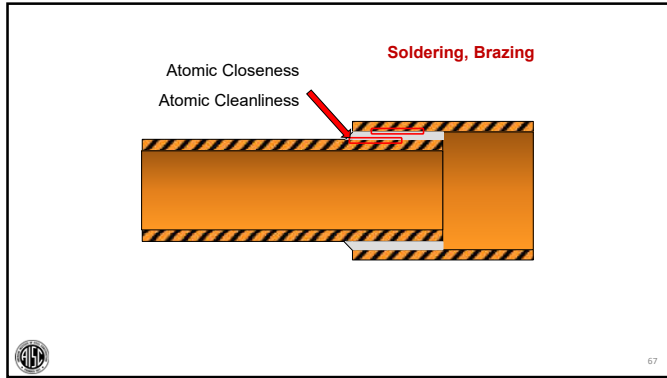

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)

Soldering Filler Metal

A filler metal having a liquidus below 450°C [840°F] to be added in making a soldered joint.

68

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)

Brazing Filler Metal

The filler metal to be added in making a brazed joint. The filler metal has a liquidus above 450°C [840°F] and below the solidus of the base material.

69

Arc Welding Processes

How to protect the metal puddle from the atmosphere:

- Inert gasses that displace the atmosphere
- Slags that form a mechanical barrier
- Both slags and gasses

70

Arc Welding Processes

Once a puddle is formed...
...the puddle must be protected from the atmosphere.

- 80% Nitrogen
- 19% Oxygen

(Also, need to protect the metal droplets in the arc)

71

Arc Welding Processes

Once a puddle is formed...
...need to control the shape of the puddle.


- Shielding gasses affect weld puddle surface tension (and the wetting of the puddle to the base metal)
- Slags can be used to support and shape weld puddles

72

Arc Welding Processes

Major arc welding processes:

- Shielded Metal Arc Welding (SMAW)
- Flux Core Arc Welding (FCAW)
- Gas Metal Arc Welding (GMAW)
- Submerged Arc Welding (SAW)
- Gas Tungsten Arc Welding (GTAW)
- Electroslag Welding (ESW)
- Electrogas Welding (EGW)
- Arc Stud Welding (ASW)




73

Arc Welding Processes

Major thermal cutting processes:

- Oxy-fuel Cutting (OFC)
- Plasma Arc Cutting (PAC)
- Air Arc Gouging (AAG)




74

WELDED CONNECTION BASICS

Outline

- Applicable Codes
- Arc Welding Processes – Overview
- ➔ • Welding and Thermal Cutting Processes
- Joints and Weld Types




75

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)


shielded metal arc welding (SMAW).

An arc welding process with an arc between a covered electrode and the weld pool. The process is used with shielding from the decomposition of the electrode covering, without the application of pressure, and with filler metal from the electrode.



76

Arc Welding Processes: SMAW

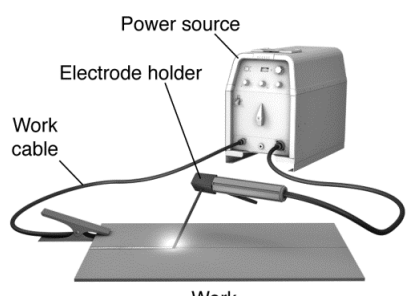


Power source

Electrode holder


Work cable


Work




77



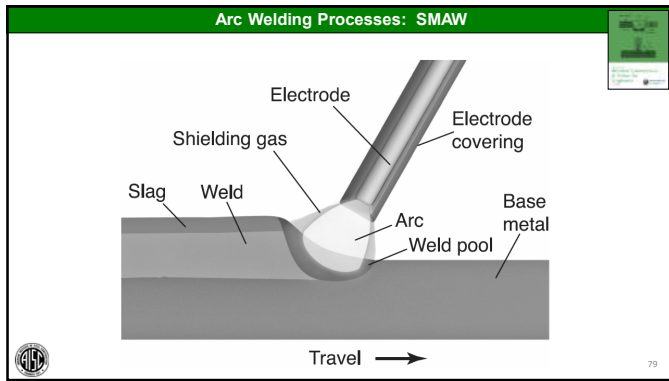


- 
- Arc Welding Processes: SMAW**
- Advantages:**
- Simplicity
 - Flexibility
 - Familiarity

- 
- Arc Welding Processes: SMAW**
- Limitations:**
- Variable resistor
 - Electrodes are of finite length
 - Stub loss
 - Operator skill required

ANSI Z49.1

Safety in Welding, Cutting, and Allied Processes

Available by free download from AWS
aws.org
www.aws.org/technical/facts

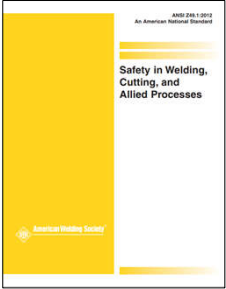


The image shows the cover of the ANSI Z49.1 standard book, titled 'Safety in Welding, Cutting, and Allied Processes'. The cover is yellow and white with the American Welding Society logo at the bottom.

The big four:

- Arc
- Fire
- Electrical
- Fume


Not comprehensive.
See Z49.1 for a complete listing

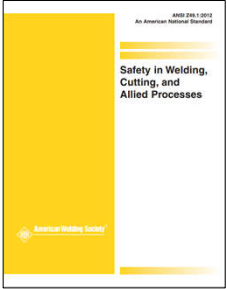

The image shows the cover of the ANSI Z49.1 standard book, titled 'Safety in Welding, Cutting, and Allied Processes'. The cover is yellow and white with the American Welding Society logo at the bottom.

AWS A5.1

Specification for Carbon Steel Electrodes
for Shielded Metal Arc Welding

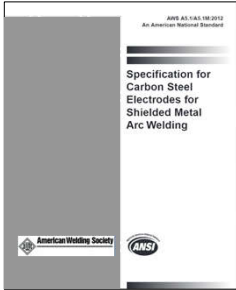

American Welding Society

85

AWS 5 Filler Metal Specifications

E7018

Electrode _____
70 ksi minimum specified tensile strength _____
1 = Position of welding _____
8 = Coating type, mechanical properties _____

86

AWS 5 Filler Metal Specifications

E4918

Electrode _____
490 MPa min. specified tensile strength _____
1 = Position of welding _____
8 = Coating type, mechanical properties _____

87


AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)

flux cored arc welding (FCAW).

An arc welding process using an arc between a continuous filler metal electrode and the weld pool. The process is used with shielding from a flux contained within the tubular electrode, with or without additional shielding gas, and without the application of pressure.

88


Arc Welding Processes: FCAW

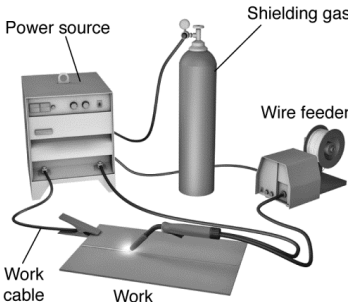

Power source
 Shielding gas
 Wire feeder
 Work cable
 Work


89

Arc Welding Processes: FCAW-G

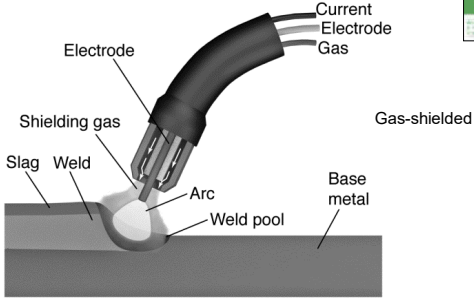

Current
 Electrode
 Gas
 Electrode
 Shielding gas
 Slag
 Weld
 Arc
 Weld pool
 Base metal
 Gas-shielded
 Travel →

90

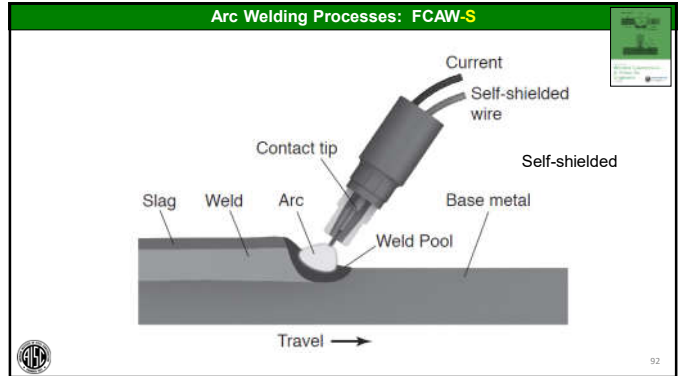

Arc Welding Processes: FCAW

Advantages:

- Electrode is continuous
 - Eliminates built-in starts and stops
 - Economic advantage
 - Starts and stops are potential sources of weld discontinuities
- Increased amperages (over SMAW)
 - Increased deposition rate and productivity
- Fixed resistance for a given electrode extension
 - More uniform welding conditions are maintained

94

Arc Welding Processes: FCAW

Advantages:

- Process is semiautomatic
 - Welders maintains the electrode extension (i.e., stickout distance) but do not need to maintain an arc length, nor do they feed the filler metal into the joint
- Process can also be mechanized or automatic

95

Arc Welding Processes: FCAW

Limitations:


- Welding equipment costs more and is less portable than for SMAW
- Changes are more complicated than for SMAW

96

Arc Welding Processes: FCAW-G

Advantages:

- More versatile than self-shielded flux-cored electrodes
- Provide better arc action
- High operator appeal
- Shielding from wind is not difficult in enclosed shop fabrication situations
- Weld appearance and quality are very good
- Higher-strength gas-shielded FCAW electrodes are available than for FCAW-S




97

Arc Welding Processes: FCAW-G

Limitations:

- The need to protect the gas shield
 - AWS D1.1 limits the maximum wind velocity to 5 mph [8 km/h]
- When welding under windy conditions, porosity is likely
- Studies have shown that at wind speeds less than 5 mph, and before onset of porosity, ductility and toughness may decrease
 - AWS D1.8 has limited maximum wind velocity to 3 mph [5 km/h]




98

Arc Welding Processes: FCAW-S

Advantages:

- Ideal when wind may disturb the gas shield (e.g., field conditions or relatively open fabrication shops)
 - Welds have been made up to 10 mph [16 km/h] without harmful effects
- No need for gas cylinders, hoses and regulators
- No concerns about gas nozzles being plugged with weld spatter
- Gun and cable assembly is simpler than for gas-shielded
 - More suitable for welding in restricted spaces




99

Arc Welding Processes: FCAW-S

Limitations:

- Technology is limited to 90 ksi [620 MPa] tensile strength or less
- Arc action not as good as FCAW-G




100

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)

gas metal arc welding (GMAW).


An arc welding process using an arc between a continuous filler metal electrode and the weld pool. The process is used with shielding from an externally supplied gas and without the application of pressure.

Note: may use solid electrode, or metal cored electrode.




101


Arc Welding Processes: GMAW

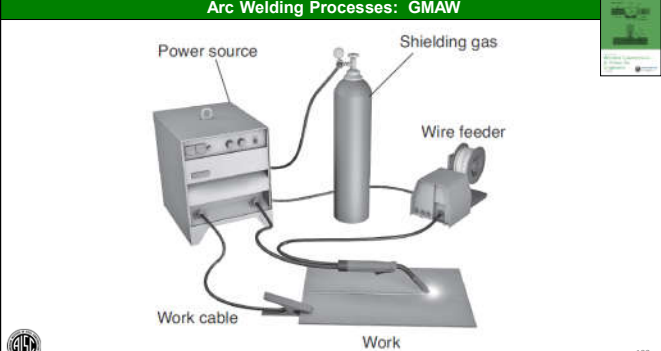


102

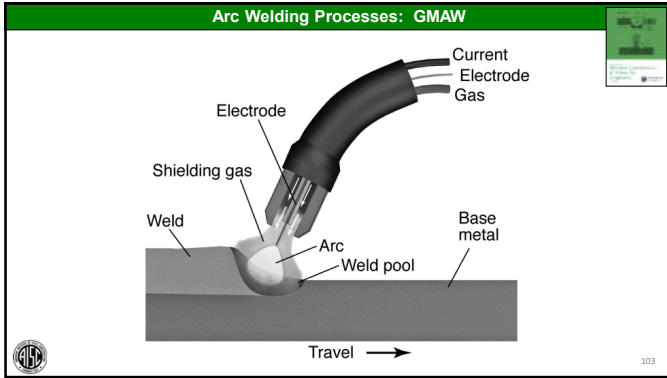

- Arc Welding Processes: GMAW**
- GMAW Modes of Metal Transfer**
- Spray
 - Globular
 - Short-Circuiting (shortarc)
 - Pulsed
- The AISC logo is in the bottom left, and the number 105 is in the bottom right.

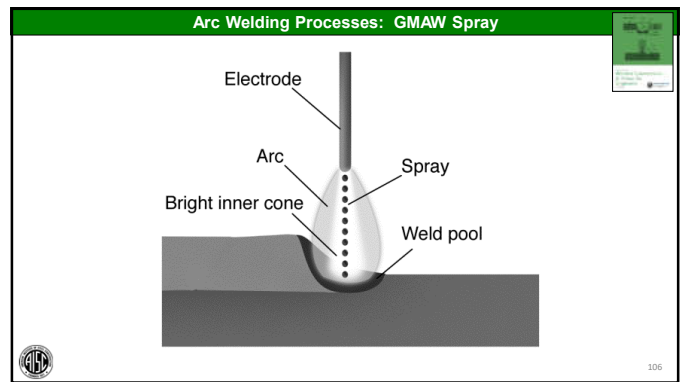

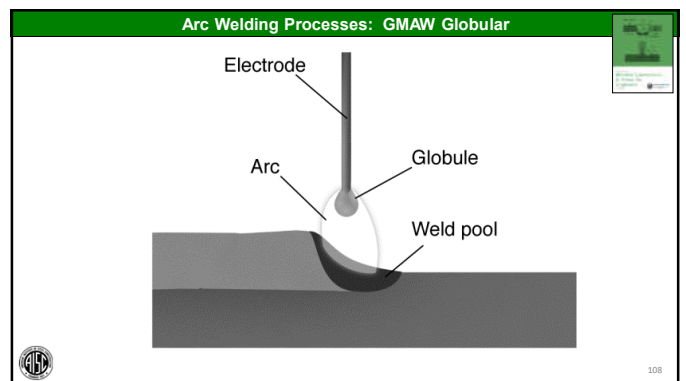

- Arc Welding Processes: GMAW**
- Mode of Transfer-dependent Advantages and Limitations:**
- Spray
 - Permits higher deposition rates and deposits welds with good appearance
 - Requires higher-cost, argon-based shielding gas mixtures, and can only be used in horizontal and flat positions
- The AISC logo is in the bottom left, and the number 107 is in the bottom right.



Arc Welding Processes: GMAW


Mode of Transfer-dependent Advantages and Limitations:

- Globular
 - Uses low-cost carbon dioxide shielding and offers high deposition rates
 - Weld appearance is inferior to spray transfer; excessive weld spatter is typical; restricted to horizontal and flat positions



109

Arc Welding Processes: GMAW Short-Circuiting

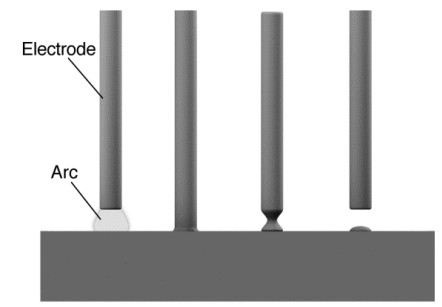

Electrode

Arc






110

Arc Welding Processes: GMAW


Mode of Transfer-dependent Advantages and Limitations:

- Short-circuit
 - Ideal for sheet metal; can be used for vertical and overhead positions
 - Strong tendency for fusion-type defects (incomplete fusion) makes it undesirable for most structural applications
 - Not prequalified in AWS D1.1
 - Welders must be qualified with the short-circuit mode of transfer



111

Arc Welding Processes: GMAW Pulsed

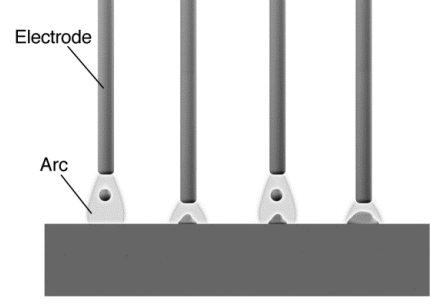

Electrode

Arc






112

Arc Welding Processes: GMAW

Mode of Transfer-dependent Advantages and Limitations:

- Pulsed
 - Permits all-position welding; deposits weld with good appearance
 - Requires use of more expensive, argon-based shielding gas mixtures
 - Welding equipment is more expensive and complex






113

Arc Welding Processes: GMAW

Advantages:

- No slag covers the weld; cleanup is simple and low cost
- Electrodes cost less than flux-cored electrodes
- Deposits welds with low levels of diffusible hydrogen
 - Significant advantage for welding on high strength steels
- Carries advantages of automatic and semiautomatic processes
 - Many robotic welding applications use GMAW, due to freedom from slag cleanup
 - Multiple-pass welding is easily accomplished






114

Arc Welding Processes: GMAW

Limitations:

- Process is more sensitive to contaminants on the steel surface (such as mill scale, rust, and oil)
 - May result in porosity
 - Heavy scale may inhibit fusion
- Limited similar to FCAW-G
 - If gas shield is disturbed, porosity will result
 - Even before onset of porosity, ductility and toughness may deteriorate





115

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2010)


submerged arc welding (SAW).

An arc welding process using an arc or arcs between a bare metal electrode and the weld pool. The arc and molten metal are shielded by a blanket of granular flux on the workpieces. The process is used without pressure and with filler metal from the electrodes and sometimes from a supplemental source (welding rod, flux, or metal granules).





116

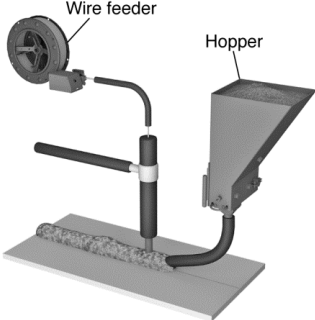Arc Welding Processes: SAW




Wire feeder

Hopper



117

Arc Welding Processes: SAW

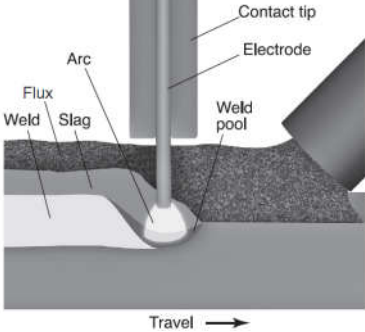

Contact tip

Electrode

Arc



Flux

Weld

Slag

Weld pool

Travel →



118





Arc Welding Processes: SAW

Advantages:

- Uses higher welding currents, leading to higher productivity and deeper penetration
 - Deeper penetration may allow fillet weld sizes to be reduced or may permit the use of groove weld details that require less weld metal
- Square wave technology may further increase deposition rate without increasing current
- For higher deposition rates, a second or third electrode can be added into the system to further increase productivity
- Process is typically mechanized or automatic
 - Welds are usually continuous for length of the joint

121

Arc Welding Processes: SAW

Advantages:

- Welds made under protective layer of flux are excellent in appearance and spatter-free
 - Particularly significant for architecturally exposed structural steel (AESS)
- Freedom from the open arc
 - Welder does not need to use the standard protective helmet
 - Operations can be done in tight, restricted areas
 - Produces little smoke, therefore can be used in situations with restricted ventilation

122

Arc Welding Processes: SAW

Limitations:

- Freedom from open arc does not allow the operator to observe the weld puddle
 - When done semiautomatically, operator must learn to propel gun carefully to ensure uniform bead contour
 - Degree of skill is significant for multiple-pass welds
- Better for long, uninterrupted seams rather than short, intermittent welds
- Restricted to flat and horizontal position




123

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2020)

gas tungsten arc welding (GTAW).

An arc welding process using an arc between a tungsten electrode (nonconsumable) and the weld pool. The process is used with shielding gas and without the application of pressure.

126

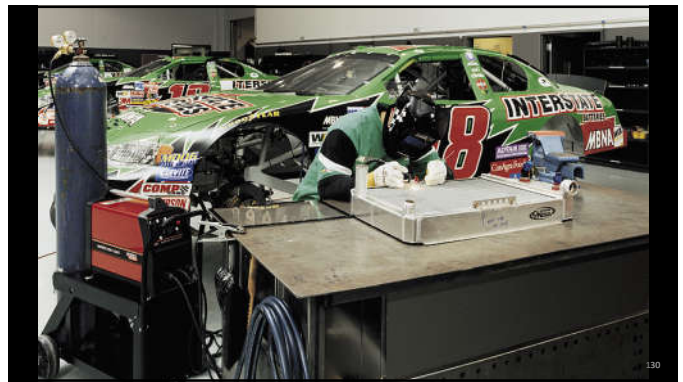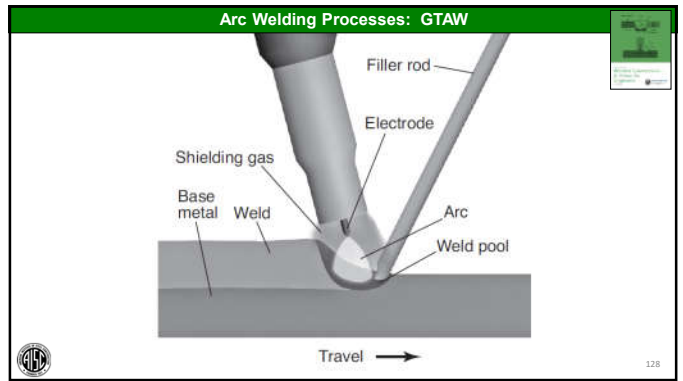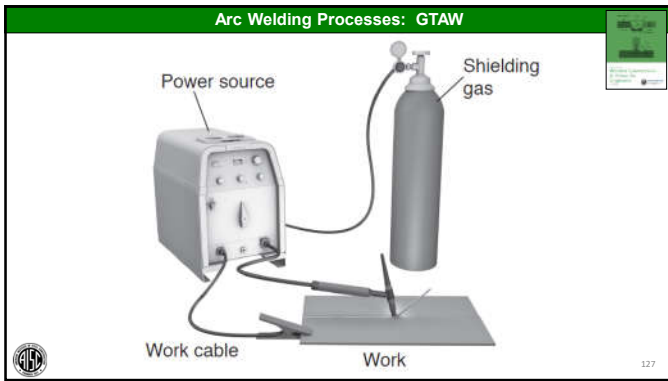

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2010)

electroslag welding (ESW).

A welding process producing coalescence of metals with molten slag, melting the filler metal and the surfaces of the workpieces. The weld pool is shielded by this slag, which moves along the full cross section of the joint as welding progresses. The process is initiated by an arc that heats the slag. The arc is then extinguished by the conductive slag, which is kept molten by its resistance to electric current passing between the electrode and the workpieces.



131

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2010)

electrogas welding (EGW).

An arc welding process using an arc between a continuous filler metal electrode and the weld pool, employing approximately vertical welding progression with backing to confine the molten weld metal. The process is used with or without an externally supplied shielding gas and without the application of pressure.




132




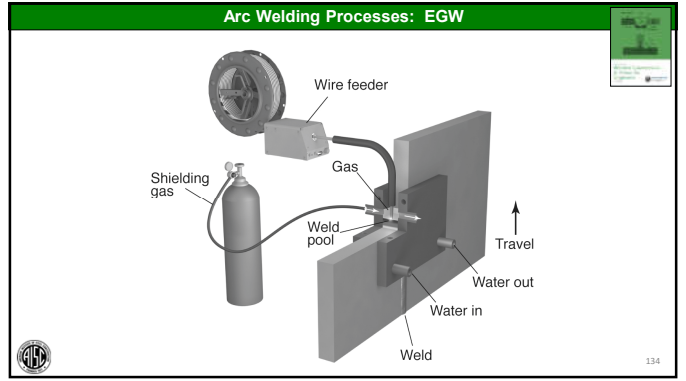
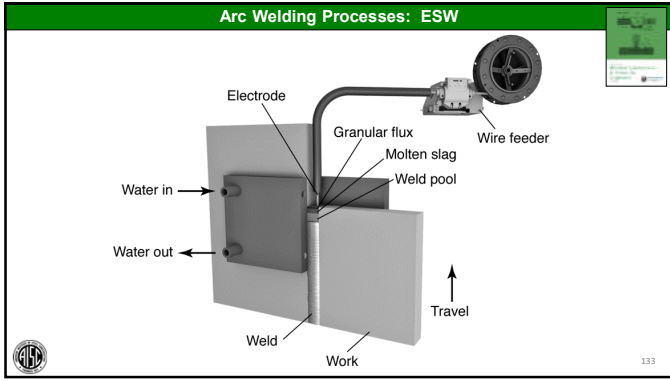


Arc Welding Processes: ESW / EGW

Applications

- "Blind welds" on box column stiffeners

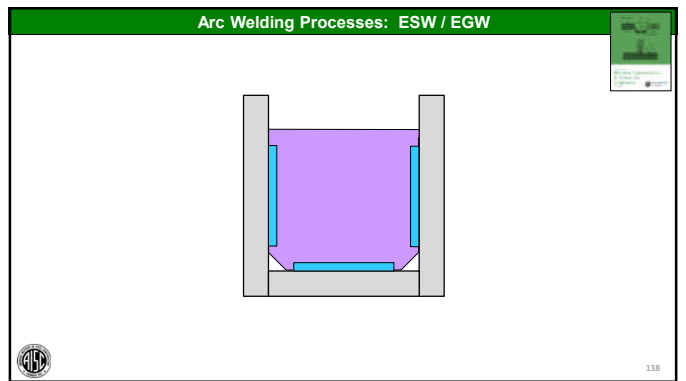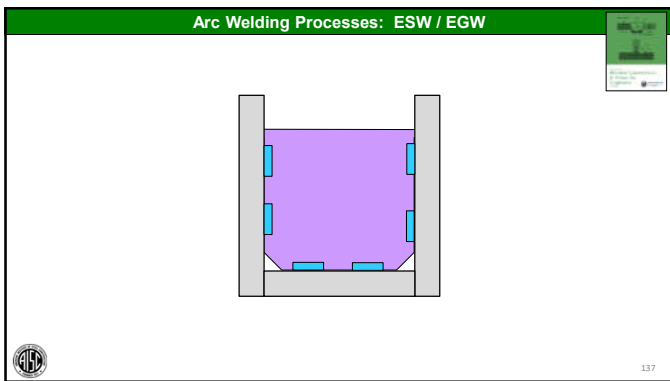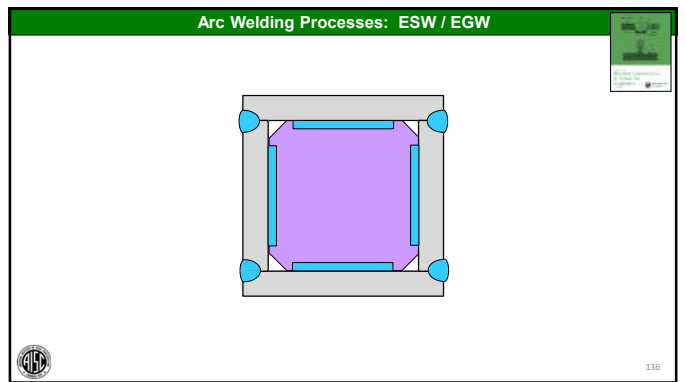

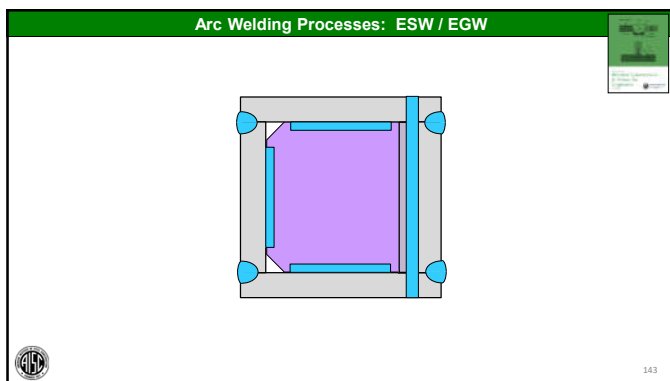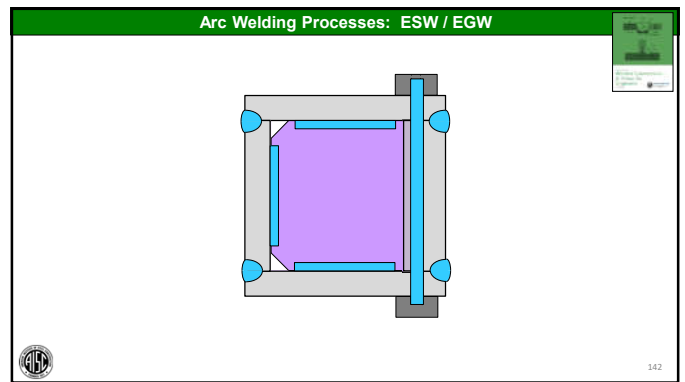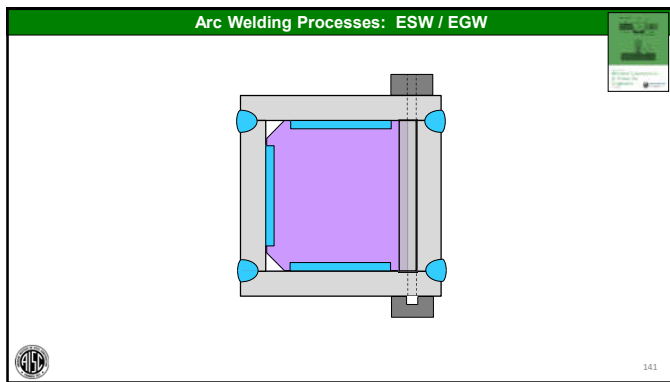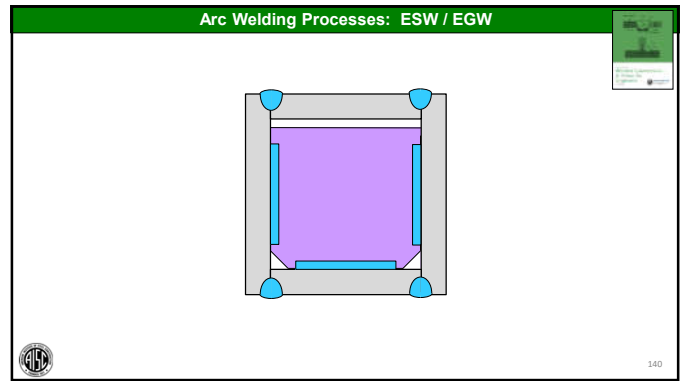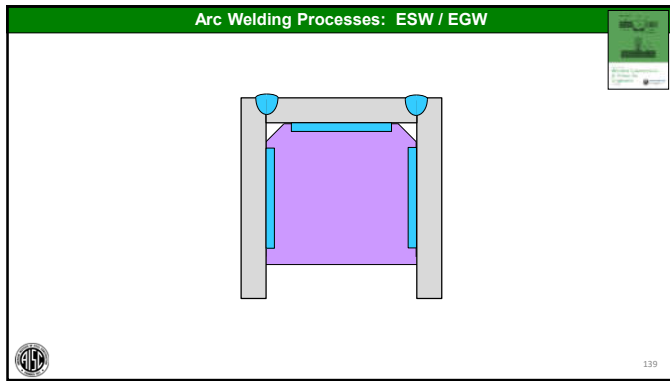

Arc Welding Processes: ESW / EGW

Applications

- "Blind welds" on box column stiffeners
- Flange splices for plate girders
- Miscellaneous applications (columns to base plates, flange plates to columns, continuity plates)



144

This slide contains a list of applications for ESW/EGW welding. The applications listed are: "Blind welds" on box column stiffeners, Flange splices for plate girders, and Miscellaneous applications (columns to base plates, flange plates to columns, continuity plates). The slide is labeled '144' in the bottom right corner.

Arc Welding Processes: ESW / EGW

Advantages:

- Very high deposition rates
- Normally, joint details involve square edges, eliminating beveling costs
- Material handling might be reduced because plates do not need to be flipped as is the case for double-sided welds made with SAW, for example
- Angular distortion can be reduced
- Advantageous for cyclically loaded structures
 - Center of the vertical weld is last to solidify, putting the face of the weld in compression, enabling better resistance to cyclic tensile stresses





145

Arc Welding Processes: ESW / EGW

Advantages:

- Ability to weld in blind joints (e.g., diaphragm plates in box columns)
 - Can weld through a hole in the box
- Ideal for welding on thicker materials (1 in. [25 mm] or greater)





146

Arc Welding Processes: ESW / EGW

Limitations:

- Not well-suited for thinner materials
- Equipment and fixturing are more expensive and less flexible
- Sensitive process with many variables
 - Specific operator training is required
 - AWS D1.1 requires all ESW and EGW welding procedure specifications be qualified by test
 - Different variables: fit of copper shoes to the work, temperature of the shoes, thickness of the slag layer
- Large heat affected zone and potentially low fracture toughness of welds





147

AWS STANDARD WELDING TERMS & DEFINITIONS (A3.0:2010)




arc stud welding (SW).

An arc welding process using an arc between a metal stud, or similar part, and the other workpiece. The process is used without filler metal, with or without shielding gas or flux, with or without partial shielding from a ceramic or graphite ferrule surrounding the stud, and with the application of pressure after the faying surfaces are sufficiently heated.






148

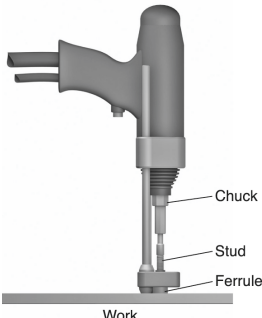Arc Welding Processes: SW













149







Thermal Cutting Processes: Oxyfuel Cutting




150

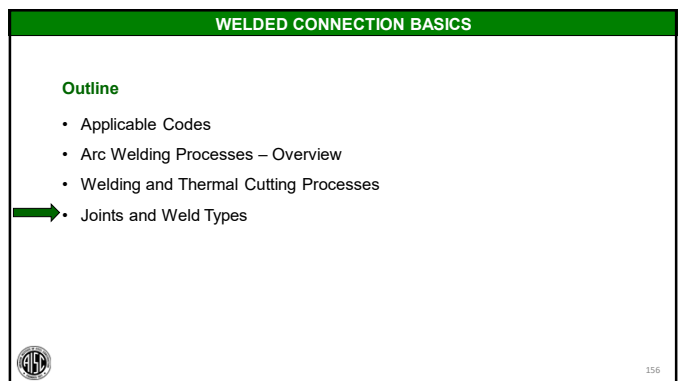
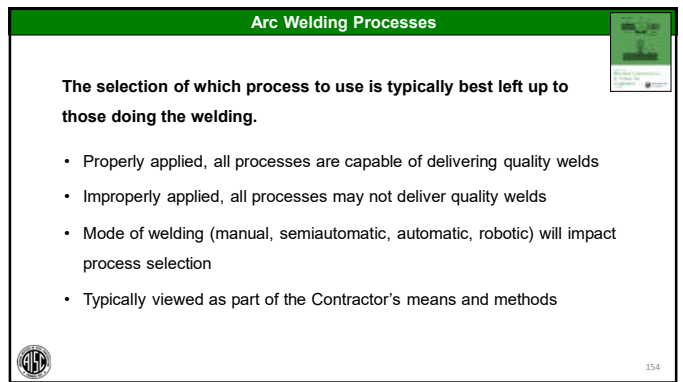
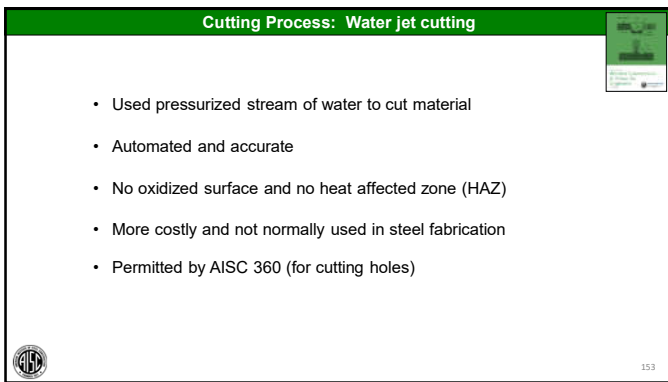
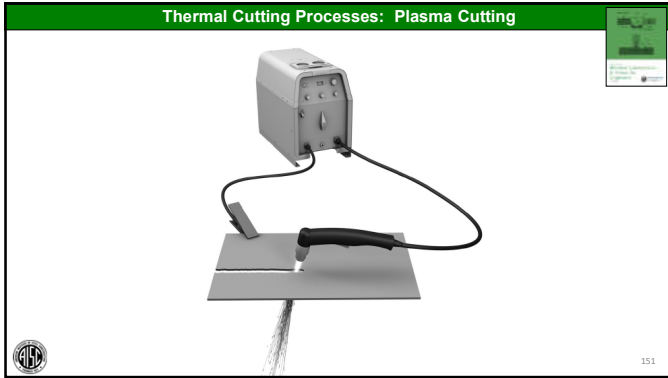


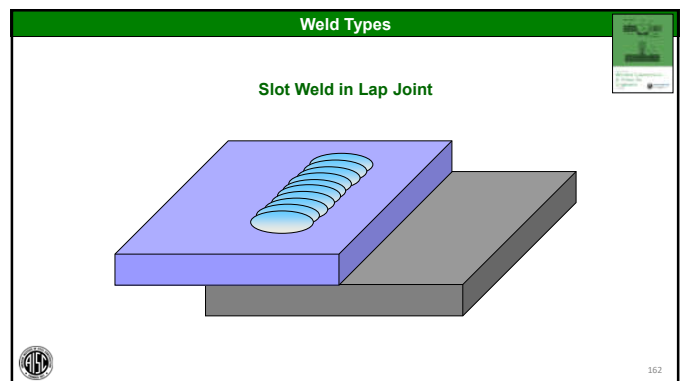
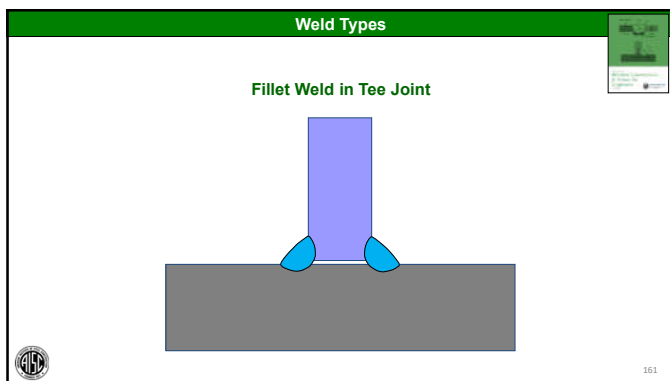
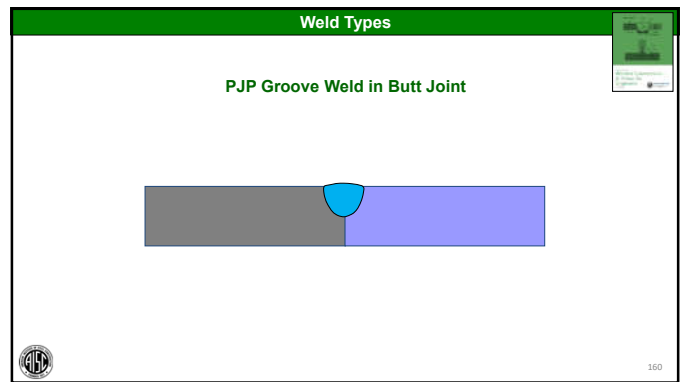
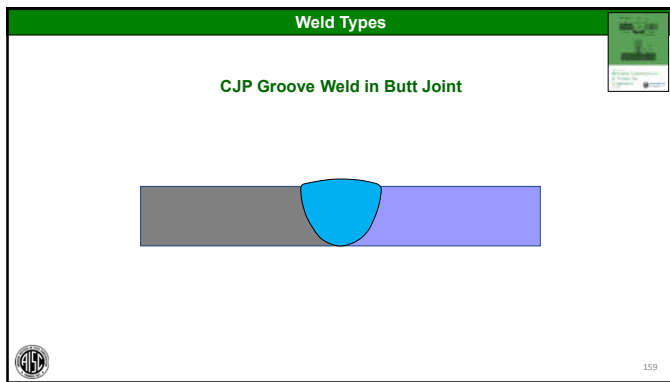
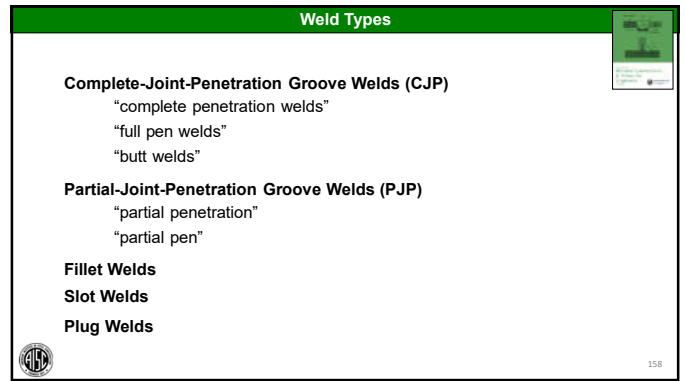
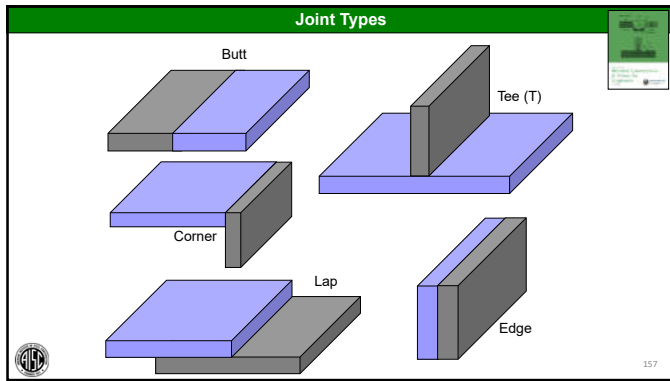


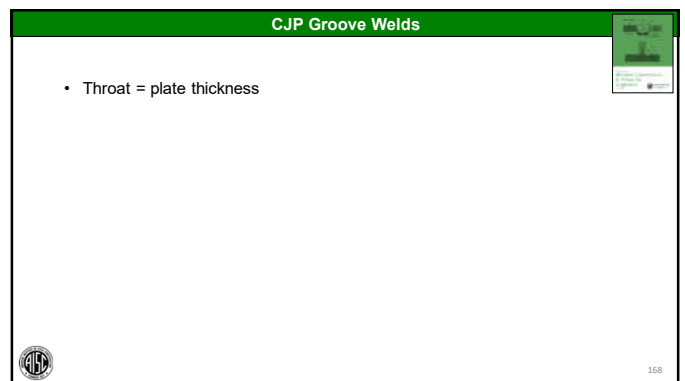
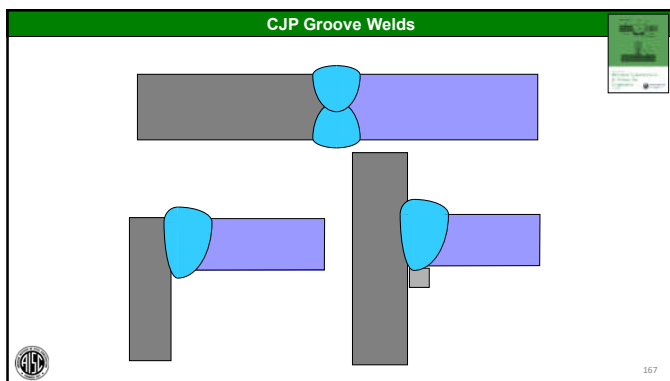
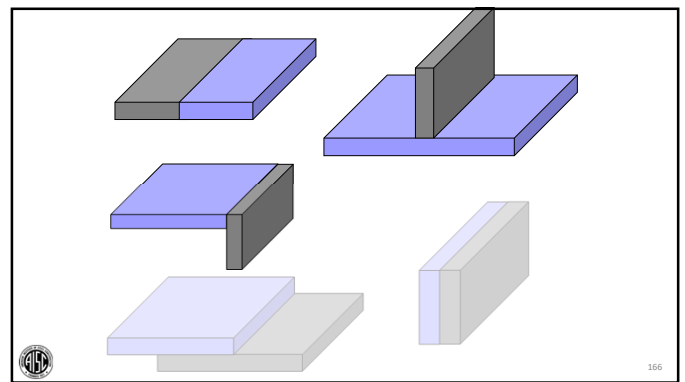
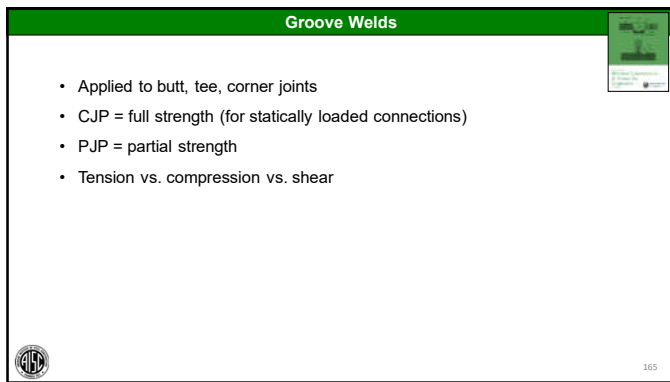
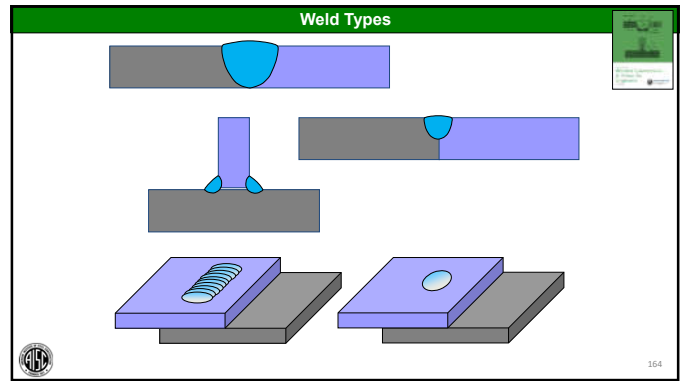
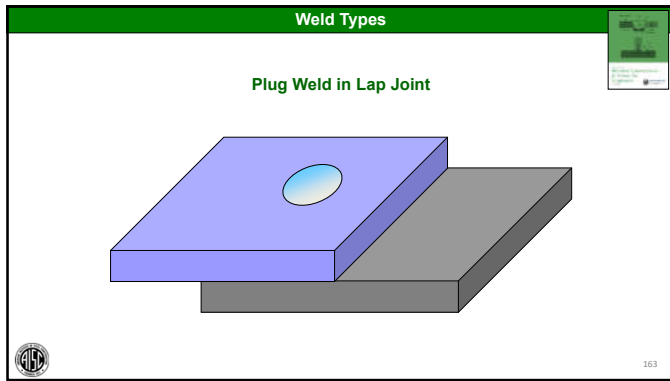







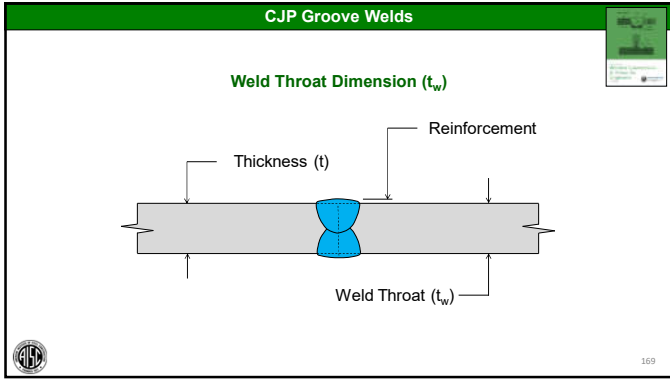








- CJP Groove Welds**
- Throat = plate thickness
 - No design calculations are required for statically loaded connections, when "matching" filler metal is used
- 170
- The AISC logo is in the bottom left corner.

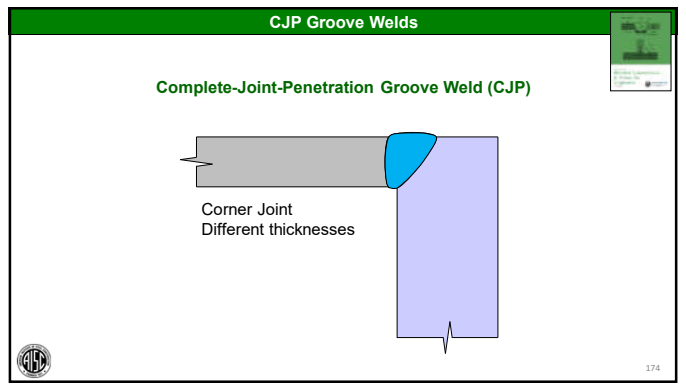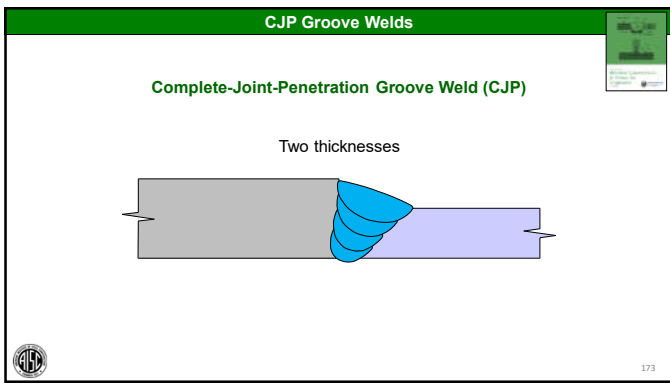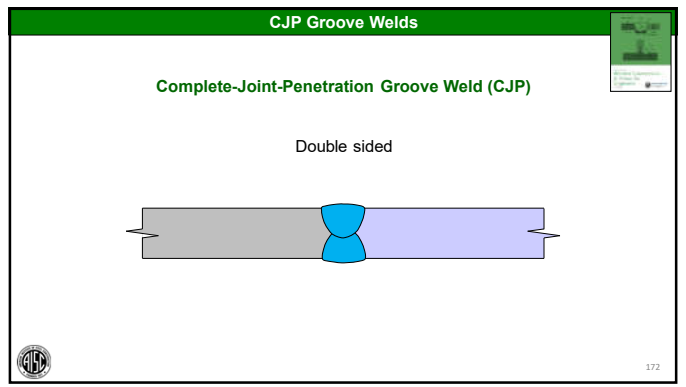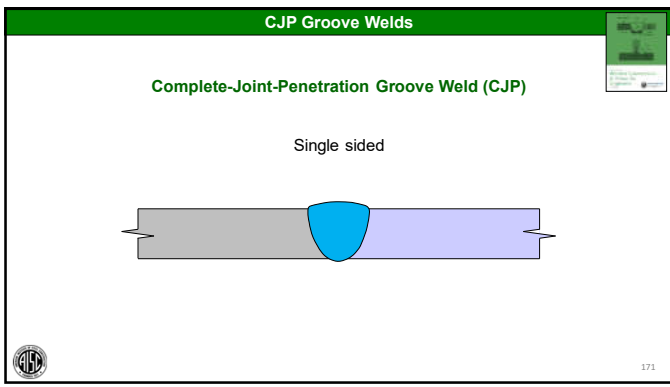

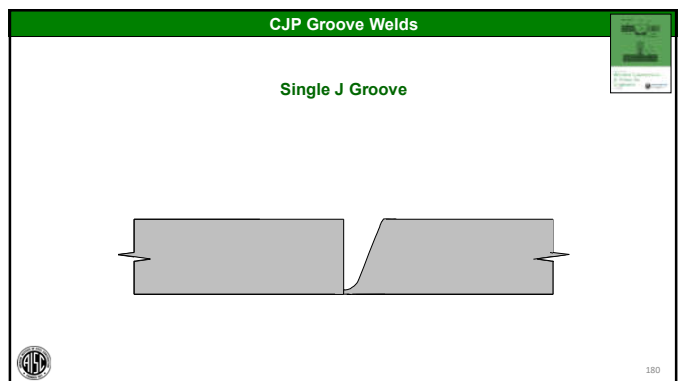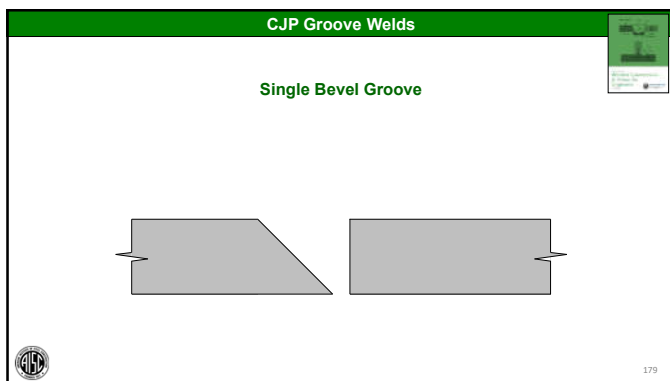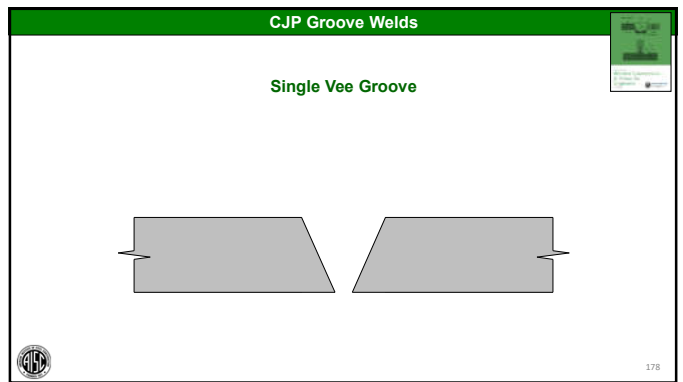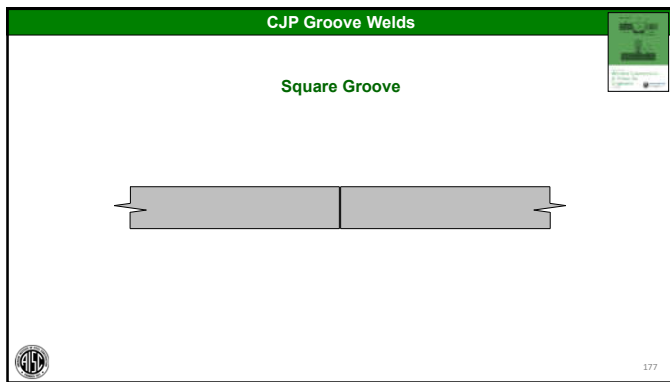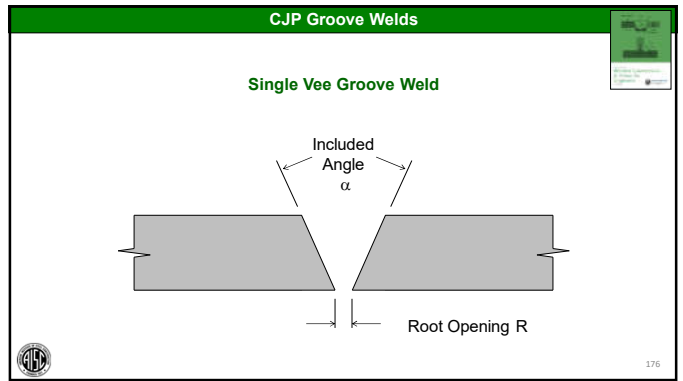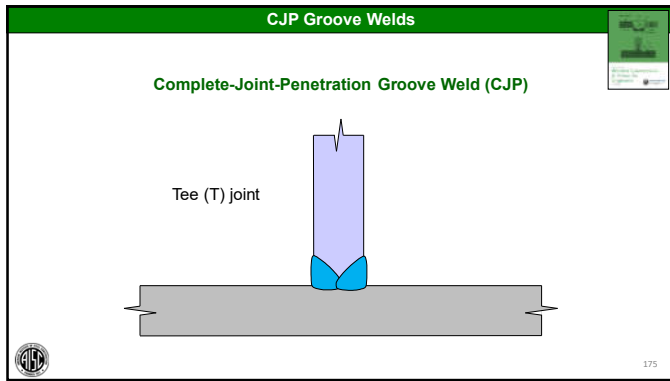

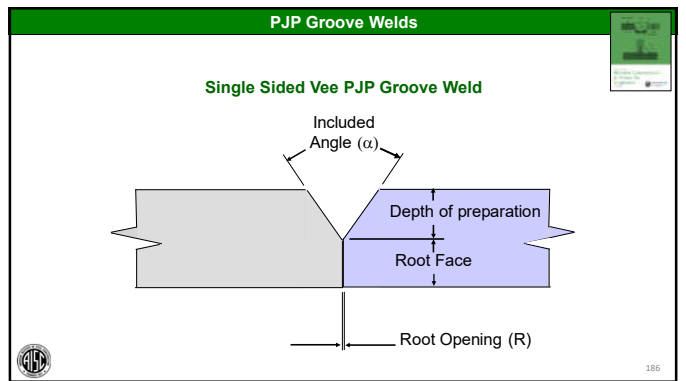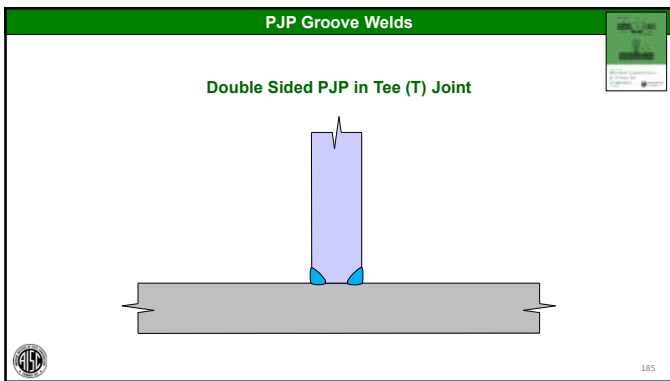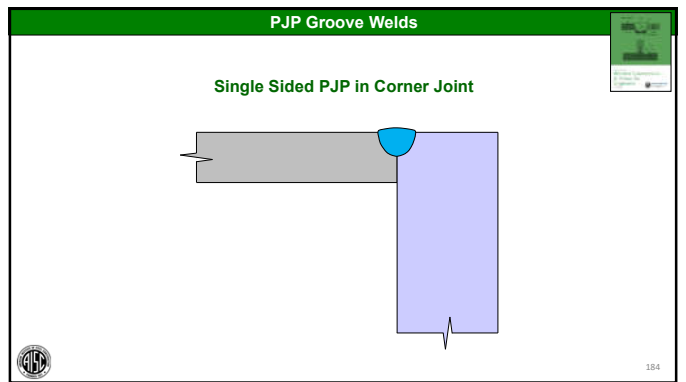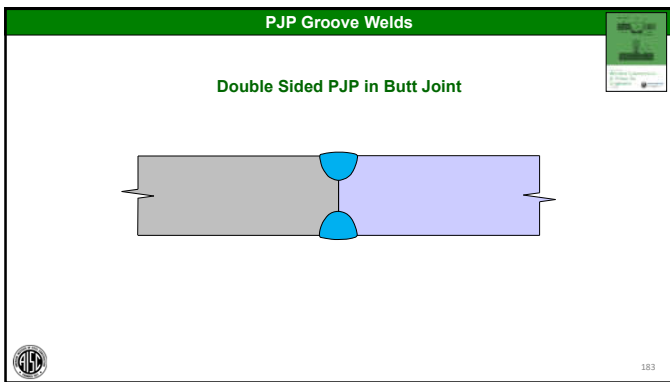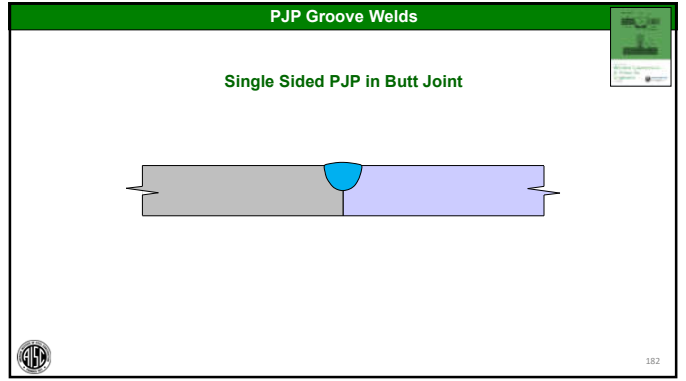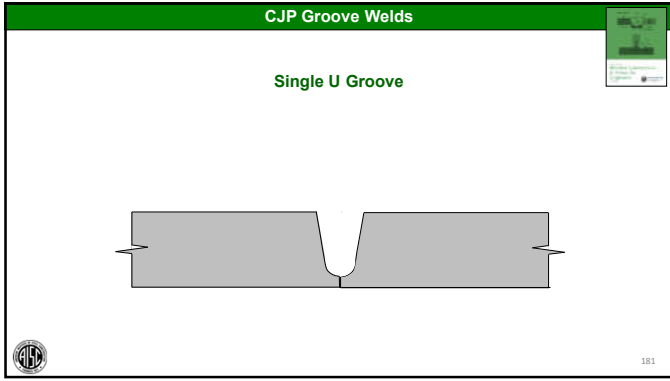

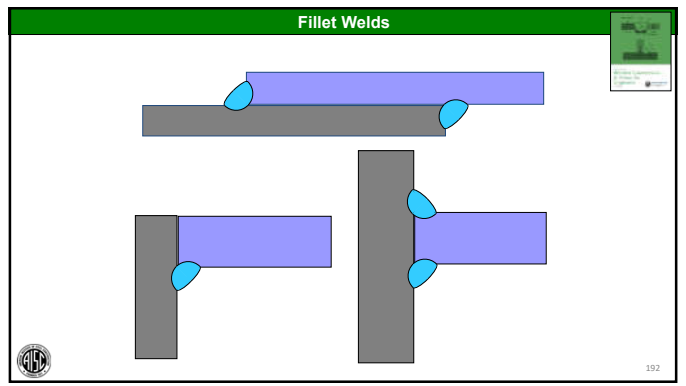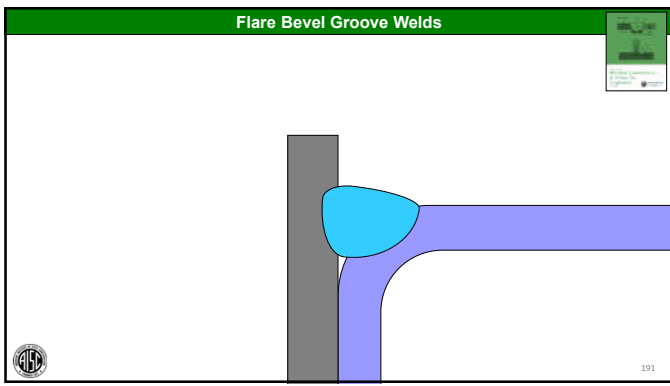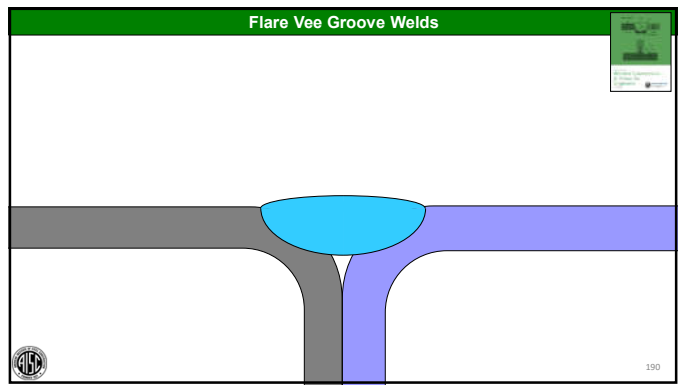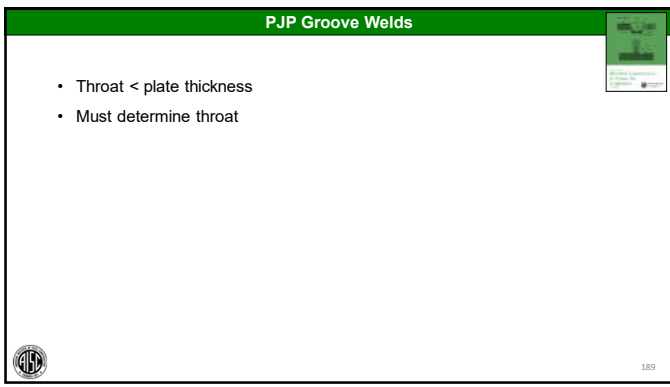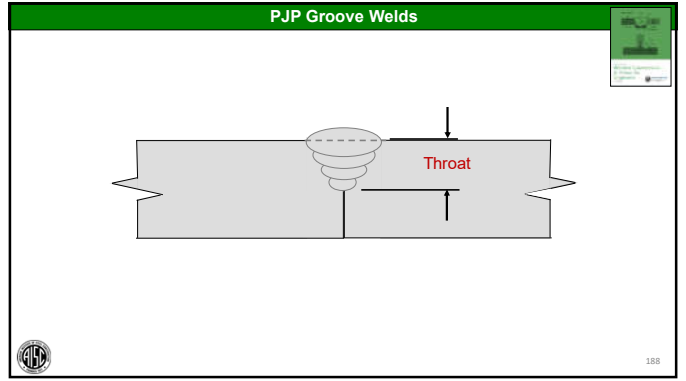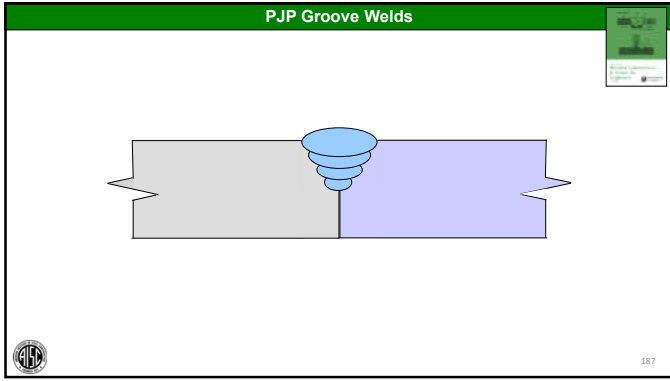

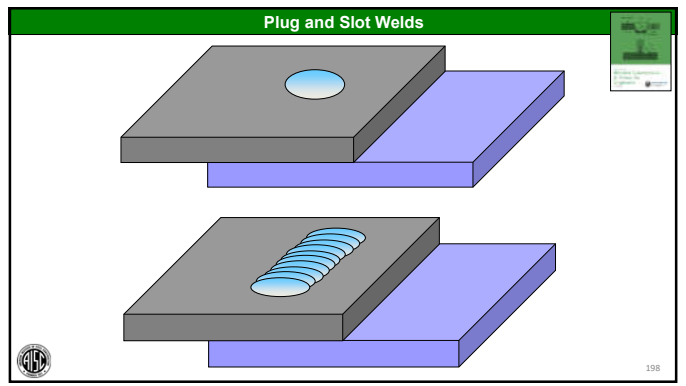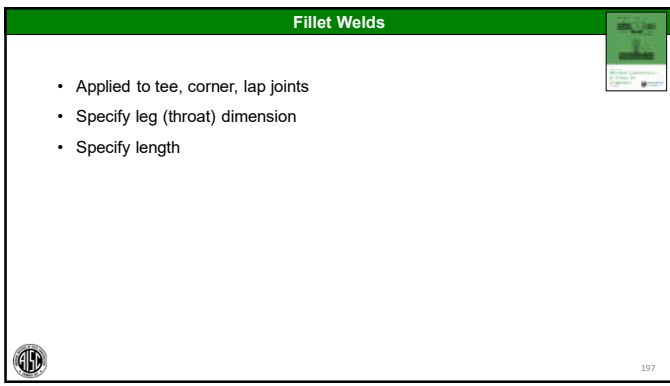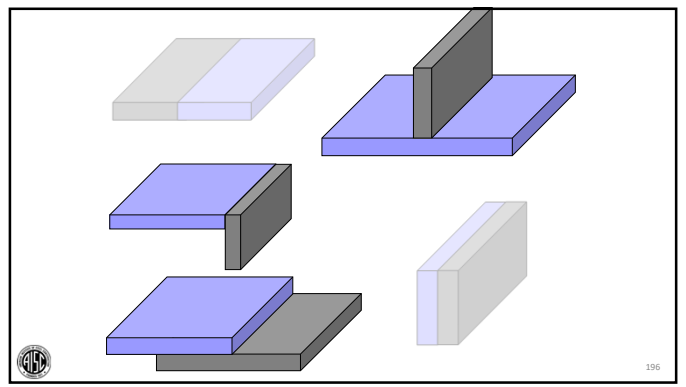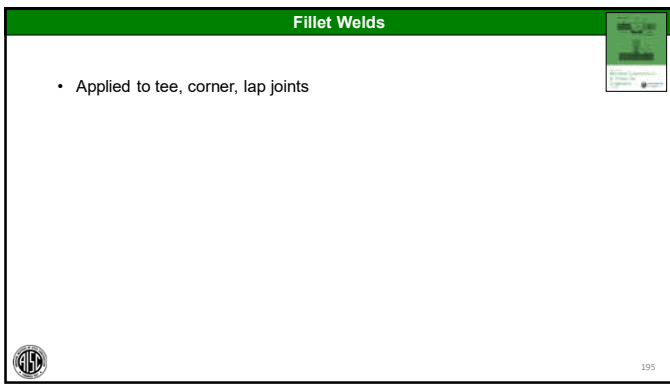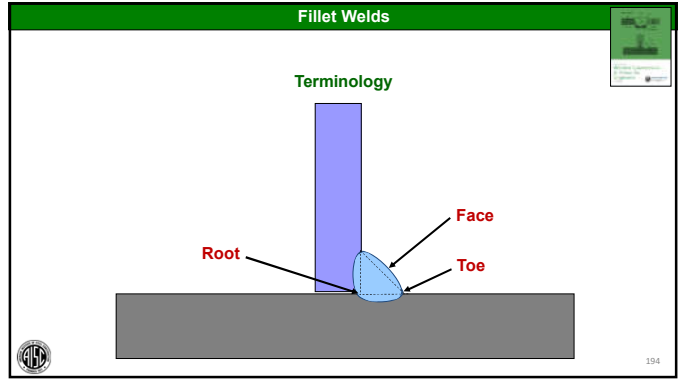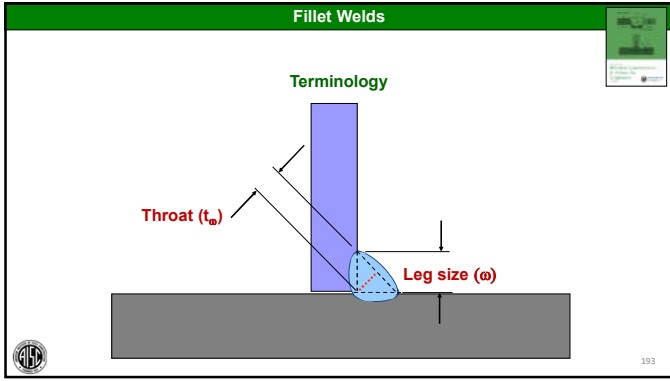




Plug and Slot Welds

- Applied to lap joints



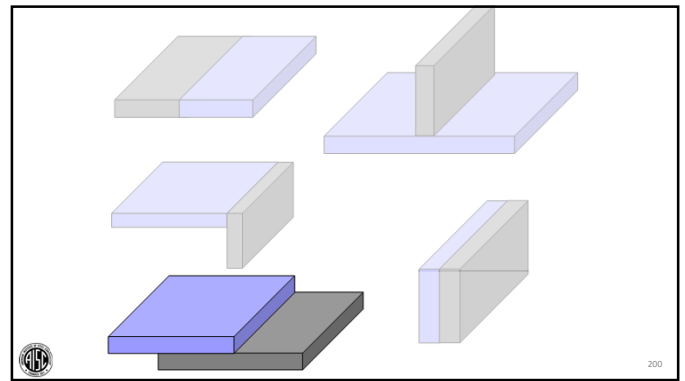

199



Plug and Slot Welds

- Applied to lap joints
- Not often applied in structures
- Restricted capacity in cyclically loaded structures




201

WELDED CONNECTION BASICS

Outline


- Applicable Codes
- Arc Welding Processes – Overview
- Welding and Thermal Cutting Processes
- Joints and Weld Types



202

Thank you!

AISC | Questions




Smarter.
Stronger.
Steel.

Individual Session Registrants

PDH Certificates


- All WFH individuals associated with a group registration will be issued a certificate.
- All individuals attending at your connection: you will receive an email on how to report their attendance from: registration@aisc.org.
 - Be on the lookout: Check your spam filter! Check your junk folder!
 - Completely fill out online form. Don't forget to check the boxes next to each attendee's name!



8-Session Registrants

PDH Certificates

One certificate will be issued at the conclusion of all 8 sessions.



8-Session Registrants

Access to the quiz

Information for accessing the quiz will be emailed to you by Thursday. It will contain a link to access the quiz. EMAIL COMES FROM NIGHTSCHOOL@AISC.ORG.


Quiz and attendance records

Posted Thursday mornings. www.aisc.org/nightschool -- Click on Current Course Details.

Reasons for quiz

- EEU – You must take all quizzes and the final exam to receive EEU.
- PDHs – If you watch a recorded session, you must pass quiz for PDHs.
- REINFORCEMENT – Reinforce what you learn tonight. Get more out of the course.

Note: If you attend the live presentation, you do not have to take the quizzes to receive PDHs




8-Session Registrants

Access to the recording

Information for accessing the recording will be emailed to you by Thursday. The recording will be available for four weeks. (For 8-session registrants only.) EMAIL COMES FROM NIGHTSCHOOL@AISC.ORG.

PDHs via recording


If you watch a recorded session, you must take *and pass* the quiz for PDHs.



8-Session Registrants

Night School Resources


Find all your handouts, quizzes and quiz scores, recording access, and attendance information all in one place!



8-Session Registrants

Night School Resources


Go to www.aisc.org and sign in.

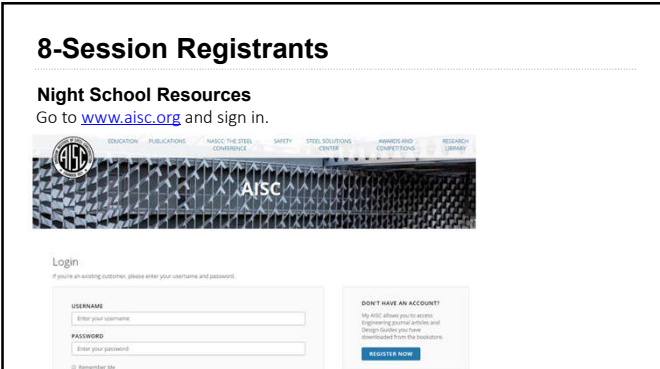

8-Session Registrants

Night School Resources

Go to www.aisc.org and sign in.

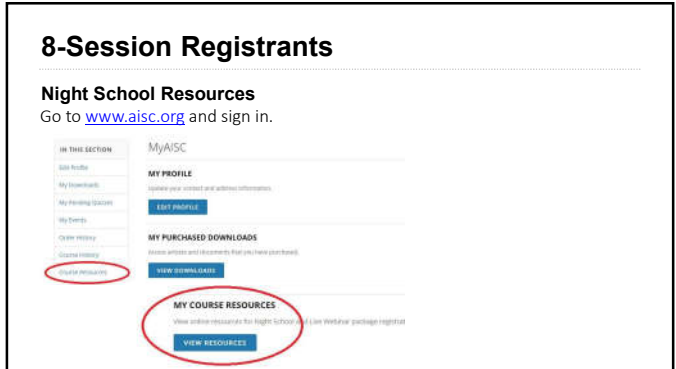

8-Session Registrants

Night School Resources

Course Resources

| Name | Start Time |
|---|-------------------------|
| NS 13 Session Design Night School 1: Design of Industrial Buildings | 6:00:00 PM - 7:00:00 PM |
| NS 13 8-Session Package Night School 1: Fundamentals of Design | 6:00:00 PM - 7:00:00 PM |

8-Session Registrants

Night School Resources

Night School 13: Design of Industrial Buildings


8-SESSION PACKAGE RESOURCES

| Event | Date | Available | Open | Start | Attendance |
|---|----------------------|-----------|------|---------|------------|
| NS13 - Design Office | 1/19/2017 7:00:00 PM | 20170119 | 2017 | 7:00:00 | 7:00:00 |
| NS13 - Economic Considerations | 2/6/2017 7:00:00 PM | 20170206 | 2017 | 7:00:00 | 7:00:00 |
| NS13 - Lateral Load Systems and Details | 2/13/2017 7:00:00 PM | 20170213 | 2017 | 7:00:00 | 7:00:00 |
| NS13 - Moment-Resisting Connections | 2/20/2017 7:00:00 PM | 20170220 | 2017 | 7:00:00 | 7:00:00 |
| NS13 - Crane Girders Design and Frame Analysis | 3/6/2017 7:00:00 PM | 20170306 | 2017 | 7:00:00 | 7:00:00 |
| NS13 - Heavy Beams and Composite Design | 3/13/2017 7:00:00 PM | 20170313 | 2017 | 7:00:00 | 7:00:00 |
| NS13 - Transfer Crane Girders & Longitudinal Rig Beams Design | 3/20/2017 7:00:00 PM | 20170320 | 2017 | 7:00:00 | 7:00:00 |
| NS13 - Building Protection and Bracing Design | 3/27/2017 7:00:00 PM | 20170327 | 2017 | 7:00:00 | 7:00:00 |

8-Session Registrants

Night School Resources



- Weekly “quiz and recording” email.
- Weekly updates of the master quiz and attendance record, found at www.aisc.org/nightschool26. Scroll down to Quiz and Attendance records.
 - Updated on Friday mornings.




8-Session Registrants

Night School Resources

- Webinar connection information
 - Reminder email sent out Tuesday mornings
- Links to handouts also found here

AISC | Thank you



Smarter.
Stronger.
Steel.